

AFRL-SN-WP-TP-2002-100

**EXTENDED MID-INFRARED (IR) TUNING OF
A Cr²⁺:CdSe LASER**

**Kenneth L. Schepler
Jason B. McKay
Won B. Roh**



OCTOBER 2001

Approved for public release; distribution unlimited.

This material is declared a work of the U.S. Government and is not subject to copyright protection in the United States.

20020419 121


**SENSORS DIRECTORATE
AIR FORCE RESEARCH LABORATORY
AIR FORCE MATERIEL COMMAND
WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7318**


NOTICE


USING GOVERNMENT DRAWINGS, SPECIFICATIONS, OR OTHER DATA INCLUDED IN THIS DOCUMENT FOR ANY PURPOSE OTHER THAN GOVERNMENT PROCUREMENT DOES NOT IN ANY WAY OBLIGATE THE U.S. GOVERNMENT. THE FACT THAT THE GOVERNMENT FORMULATED OR SUPPLIED THE DRAWINGS, SPECIFICATIONS, OR OTHER DATA DOES NOT LICENSE THE HOLDER OR ANY OTHER PERSON OR CORPORATION; OR CONVEY ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE, OR SELL ANY PATENTED INVENTION THAT MAY RELATE TO THEM.

THIS REPORT IS RELEASABLE TO THE NATIONAL TECHNICAL INFORMATION SERVICE (NTIS). AT NTIS, IT WILL BE AVAILABLE TO THE GENERAL PUBLIC, INCLUDING FOREIGN NATIONS.

THIS TECHNICAL REPORT HAS BEEN REVIEWED AND IS APPROVED FOR PUBLICATION.


KENNETH L. SCHEPLER
Principal Scientist
EO Countermeasures Technology Branch


JOSEPH KOESTERS, Chief
EO Countermeasures Technology Branch
EO Sensor Technology Division


STEVEN R. PETERSEN, Colonel, USAF
EO Sensor Technology Division
Sensors Directorate

Do not return copies of this report unless contractual obligations or notice on a specific document require its return.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 074-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE October 2001		3. REPORT TYPE AND DATES COVERED Preprint, 04/01/2001 – 10/01/2001
4. TITLE AND SUBTITLE Extended Mid-Infrared (IR) Tuning of a Cr ²⁺ :CdSe Laser			5. FUNDING NUMBERS C: In-House PE: 61102F PR: 2301 TA: EL WU: 01	
6. AUTHOR(S) Kenneth L. Schepler (AFRL) Jason B. McKay (AFIT) Won B. Roh (AFIT)				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Air Force Research Laboratory 3109 P. Street WPAFB, OH 45433			8. PERFORMING ORGANIZATION REPORT NUMBER Air Force Institute of Technology 2950 P. Street WPAFB, OH 45433	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) SENSORS DIRECTORATE AIR FORCE RESEARCH LABORATORY AIR FORCE MATERIEL COMMAND WRIGHT-PATTERSON AIR FORCE BASE, OH 45433-7318 POC: Kenneth L. Schepler, AFRL/SNJW, (937) 255-3804 x274			10. SPONSORING / MONITORING AGENCY REPORT NUMBER AFRL-SN-WP-TP-2002-100	
11. SUPPLEMENTARY NOTES This material is declared a work of the U.S. Government and is not subject to copyright protection in the United States. Article submitted for publication to The Optical Society of America in their Trends in Optics and Photonics Series.				
12a. DISTRIBUTION / AVAILABILITY STATEMENT Approved for public release; distribution unlimited.				12b. DISTRIBUTION CODE
13. ABSTRACT (Maximum 200 Words) We report 2450-3400 nm laser operation from a Cr ²⁺ :CdSe laser, pumped by a Q-switched Tm,Ho:YLF laser. Laser turning was achieved over a large part of the 2100-3400 nm emission cross section bandwidth using a simple grating-tuned resonator.				
14. SUBJECT TERMS Lasers, infrared, cadmium selenide, chromium, broad tuning				15. NUMBER OF PAGES 10
				16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT SAR	

NSN 7540-01-280-5500

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-18
298-102

Extended Mid-IR Tuning of a Cr^{2+} :CdSe Laser

Jason B. McKay and Won B. Roh

*Air Force Institute of Technology, 2950 P. St., WPAFB OH 45433
Phone: (937) 255-5922 x267, Email: Jason.mckay@wpafb.af.mil*

Kenneth L. Schepler

*Air Force Research Laboratory, 3109 P St., WPAFB, OH 45433
Phone: (937) 255-5922 x274, Email: kenneth.schepler@wpafb.af.mil*

Abstract: We report 2450-3400 nm laser operation from a Cr^{2+} :CdSe laser, pumped by a Q-switched Tm,Ho:YLF laser. Laser tuning was achieved over a large part of the 2100-3400 nm emission cross section bandwidth using a simple grating-tuned resonator.

OCIS Codes: (140.5680) Rare earth and transition metal solid-state lasers; (140.3070) Infrared and far-infrared lasers

1. Introduction

Research over the past few years[1-4] has shown Cr^{2+} :chalcogenide II-VI materials to have the potential for broad tuning in the mid-infrared. The possibility of a single laser that could tune from 2-3.5 μm has been of interest for applications in spectroscopy and chemical detection. However until this time no Cr^{2+} laser has tuned out farther than 3.04 μm [5]. Thermal effects in Cr^{2+} materials at moderate absorbed power levels and limitations of optical coatings have prevented laser operation in the long wavelength tail of the emission spectra. By going to a simple resonator with extremely broadband optics, using a large diameter pump beam, and operating at a pulse repetition rate slow enough to mitigate thermal effects, we have demonstrated long wavelength operation of Cr^{2+} :CdSe out to 3.4 μm .

2. Cr^{2+} :CdSe Sample

The crystal used for this demonstration was a 12-mm long, diffusion-doped Cr^{2+} :CdSe sample made and anti-reflection coated by Cleveland Crystals. This sample absorbed 63% of incident 2.05- μm pump light, and was AR coated for 2.4-2.9 μm operation. In earlier work, crystals from the same batch as this sample have shown tuning from 2.3-2.9 μm [3]. Typical losses in these samples were ~5% per pass at the lasing wavelengths.

3. Emission Cross Section Measurement

To investigate the feasibility of extended tuning past 3 μm in Cr^{2+} :CdSe, the emission cross section was measured using a PbSe detector and a 15-cm spectrometer calibrated to a blackbody reference source. With slit spacings of $\frac{1}{4}$ mm (limited by detector sensitivity), the effective resolution was ~20 nm FWHM, adequate for measurement of Cr^{2+} broadband fluorescence. Fluorescence from Cr^{2+} :CdSe was measured, under 1-W CW excitation by a 2.05- μm Tm,Ho:YLF laser. Cr^{2+} :ZnSe fluorescence was measured as well, for comparison purposes. The fluorescence data were then used to produce the emission lineshape function, which was used along with the fluorescence lifetime to calculate the emission cross section. The emission cross sections for Cr^{2+} in CdSe and ZnSe calculated by this method are shown in Fig. 1. Note that the emission cross section for Cr:CdSe extends to much longer wavelengths than that of Cr:ZnSe, allowing for the possibility of extended tuning in the mid-infrared past 3.4 μm . Note that it does not appear likely that Cr^{2+} :ZnSe would tune out past 3 μm without exceptionally intense pumping.

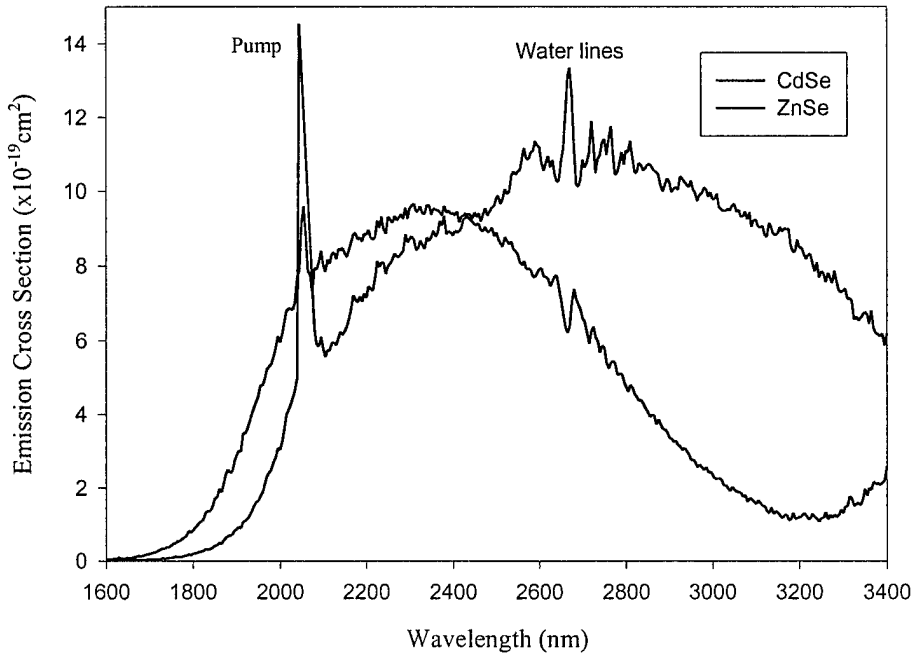


Figure 1. Cr^{2+} Emission Cross Sections. Increasing trend beyond $3.2 \mu\text{m}$ in ZnSe is due to 2nd order diffraction of short wavelength emission.

4. Cr:CdSe Laser Tuning

The laser tuning experimental setup consisted of a simple end-pumped Cr^{2+} :CdSe standing wave laser using a Tm,Ho:YLF laser for excitation, a diffraction grating for tuning, and a 15-cm spectrometer and pyroelectric detector for wavelength measurements. A schematic of the setup is shown in Fig. 2. The Tm,Ho:YLF laser was Q-switched at 3 kHz (400 ns FWHM pulses) and focused to a 1-mm beam diameter inside the Cr:CdSe rod. The laser rod was held in a water-cooled heat sink. Positive thermal lensing inside the laser rod provided the cavity stability. The output from the Cr^{2+} :CdSe laser was the ~20% specular reflection from the diffraction grating, and the feedback was provided by the first order diffraction. Changing the grating angle changed the Cr^{2+} :CdSe laser wavelength. The output was sent through a 15-cm monochromator and detected by a chopped pyroelectric power meter.

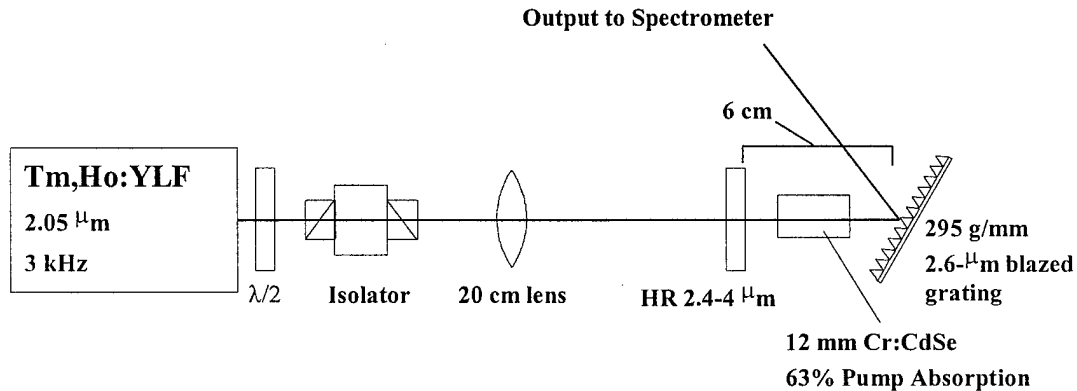


Figure 2. Tuning Experiment Setup

The absorbed power laser threshold of the Cr^{2+} :CdSe laser was measured as a function of output wavelength. The result is shown in Fig. 3. The experiment validates the emission cross section

measurements which indicate significant gain out to long wavelengths past 3 μm . A broad tuning range of 2450 to 3400 nm was demonstrated, the longest wavelength tuning yet achieved for a Cr^{2+} laser. Tuning below 2450 nm has previously been demonstrated, but was not possible for this experiment due to a cutoff in the input coupler reflectivity at 2450 nm. With appropriate broadband optics (such as metallic mirrors), pulsed operation over the range of 2.3-3.4+ μm from the $\text{Cr}^{2+}:\text{CdSe}$ laser should be possible. The fundamental limits on the tuning range are ground state absorption at short wavelengths and the onset of thermal effects and damage at long wavelengths.

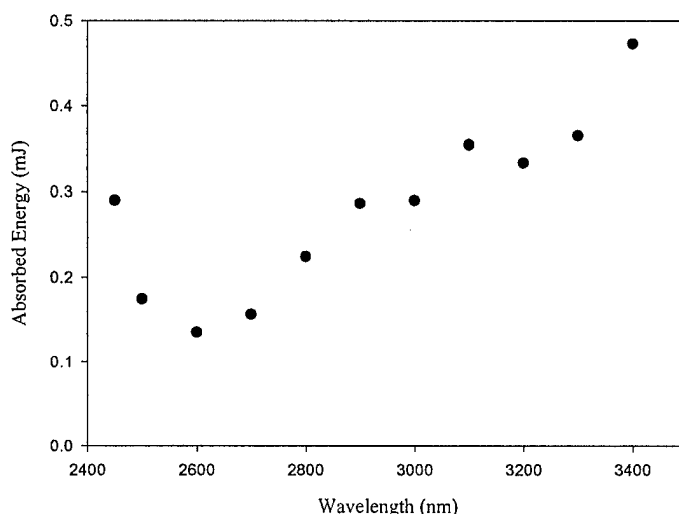


Figure 3. $\text{Cr}^{2+}:\text{CdSe}$ Laser Threshold vs. Wavelength

As shown in Fig 3, laser threshold increased towards the edges of the tuning curve due to diminishing gain. But in addition, the threshold was further increased by nonradiative relaxation and thermal lensing which increased as absorbed power increased. Past a certain absorbed power the thermal effects prevented laser operation altogether. To achieve the maximum tuning range in the experiment, we had to mitigate these thermal effects at the expense of efficiency. We used a large pump beam diameter to lessen the radial temperature gradient experienced by the cavity mode. We also used a Q-switched, 3-kHz, pump beam to reduce the average absorbed power and to reach threshold with a large beam diameter.

Our experiment was designed to demonstrate maximum tuning range. Optimizing efficiency and output power will require sophisticated compensation of thermal effects. One possible technique under consideration is thin disk cooling which reduces resonator loss and improves heat transfer out of the crystal.

5. Summary

With broadband optics, and mitigation of thermal effects, a $\text{Cr}^{2+}:\text{CdSe}$ laser tuned from 2450 nm to 3400 nm, well past the previous limit of 2.9 μm . This tuning agreement is in excellent agreement with emission cross section calculations. The broad tuning range of $\text{Cr}^{2+}:\text{CdSe}$ makes it look promising for tunable laser applications, despite its poor thermal conductivity. We plan to demonstrate useful tuning range from 2.1-3.4 μm with a thin disk approach to mitigate thermal effects and improve operating efficiency.

6. References

1. Wagner, G.J., *et al.*, *Continuous-wave broadly tunable $\text{Cr}^{2+}:\text{ZnSe}$ laser*. Optics Letters, 1999. **24**(1): p. 19-21.
2. Seo, J.T., *et al.*, *Phys. Stat. Sol. (A)*, 1999. **175**: p. R3.
3. McKay, J., K.L. Schepler, and G.C. Catella, *Efficient grating tuned mid-IR $\text{Cr}^{2+}:\text{CdSe}$ laser*. Optics Letters, 1999. **24**(22): p. 1575-1577.
4. Page, R.H., *et al.*, *Cr^{2+} -doped zinc chalcogenides as efficient, widely tunable mid-infrared lasers*. IEEE J. Quantum Electron., 1997. **33**(4): p. 609-619.
5. Mond, M., *et al.*, *Continuous Wave Diode Pumped $\text{Cr}^{2+}:\text{ZnSe}$ and High Power Laser Operation*, in *OSA Trends in Optics and Photonics, Advanced Solid State Lasers*, C. Marshall, Editor. 2001, Optical Society of America: Washington, DC. p. 162-165.